

NANO EXPRESS

Open Access

Fabrication and NO₂ gas sensing performance of TeO₂-core/CuO-shell heterostructure nanorod sensors

Sunghoon Park¹, Soohyun Kim¹, Gun-Joo Sun¹, Wan In Lee², Kyoung Kook Kim³ and Chongmu Lee^{1*}**Abstract**

TeO₂-nanostructured sensors are seldom reported compared to other metal oxide semiconductor materials such as ZnO, In₂O₃, TiO₂, Ga₂O₃, etc. TeO₂/CuO core-shell nanorods were fabricated by thermal evaporation of Te powder followed by sputter deposition of CuO. Scanning electron microscopy and X-ray diffraction showed that each nanorod consisted of a single crystal TeO₂ core and a polycrystalline CuO shell with a thickness of approximately 7 nm. The TeO₂/CuO core-shell one-dimensional (1D) nanostructures exhibited a bamboo leaf-like morphology. The core-shell nanorods were 100 to 300 nm in diameter and up to 30 μm in length. The multiple networked TeO₂/CuO core-shell nanorod sensor showed responses of 142% to 425% to 0.5- to 10-ppm NO₂ at 150°C. These responses were stronger than or comparable to those of many other metal oxide nanostructures, suggesting that TeO₂ is also a promising sensor material. The responses of the core-shell nanorods were 1.2 to 2.1 times higher than those of pristine TeO₂ nanorods over the same NO₂ concentration range. The underlying mechanism for the enhanced NO₂ sensing properties of the core-shell nanorod sensor can be explained by the potential barrier-controlled carrier transport mechanism.

Keywords: TeO₂ nanorods; CuO shells; Gas sensors; Response; NO₂**PACS:** 61.46. + w; 07.07.Df; 73.22.-f**Background**

In recent years, one-dimensional (1D) nanostructure-based sensors attracted considerable attention owing to their high surface-to-volume ratios [1-5]. Considerable effort has been made to develop 1D nanostructured gas sensors with good sensing performances, but further improvements in the sensitivity of 1D nanostructured sensors are needed. The fabrication of heterostructures [6-8] is a promising technique to improve the sensitivity of the 1D nanostructured sensors. The improved sensing performance of the heterostructured 1D sensors has been attributed to a range of factors including increased potential barriers at the interface of the heterostructure

[9,10], modulated depletion layer [11,12], band bending due to equilibration of the Fermi energy levels [13], synergistic surface reactions [14], etc.

Paratellurite (α-TeO₂) is a metal oxide semiconductor with a distorted rutile structure [15]. TeO₂ has applications in optical storage, laser devices and gas sensors, dosimeters, modulators, and deflectors owing to its unique properties such as high refractive index and high optical nonlinearity [16]. TeO₂-nanostructured sensors have attracted less attention compared to other metal oxide semiconductor materials such as ZnO, In₂O₃, TiO₂, Ga₂O₃, etc. In 2007, Liu et al. [17] synthesized TeO₂ nanowires that were sensitive to NO₂, NH₃, and H₂S gases. According to their results, TeO₂ 1D nanostructures are promising for producing low power consumption gas sensors. The incorporation of a surface

* Correspondence: cmlee@inha.ac.kr¹Department of Materials Science and Engineering, Inha University, 253 Yonghyun-dong, Nam-gu, Incheon 402-751, Republic of Korea
Full list of author information is available at the end of the article

decoration or heterostructure formation technique can improve their sensing performance further. In this regard, a recent study reported the sensing properties of Pt-doped TeO_2 nanorods [16]. On the other hand, this paper reports the synthesis of TeO_2 -core/ CuO -shell nanorods and the sensing properties of multiple networked TeO_2 -core/ CuO -shell nanorod gas sensors toward NO_2 gas. The underlying mechanism for the enhanced sensing performance of the core-shell nanorod sensors is also discussed.


Methods

TeO_2 / CuO core-shell nanorods were synthesized using a two-step process: thermal evaporation of Te powder followed by sputter deposition of CuO . TeO_2 nanorods were synthesized on a p-type Si (100) substrate in a quartz tube furnace by thermal evaporation of Te powder at 400°C in air without a metal catalyst or the supply of other gas. The thermal evaporation process was conducted at room temperature for 1 h and the furnace was cooled to room temperature. Subsequently, the TeO_2 nanorods were coated with a thin CuO layer by sputtering a CuO target by radio frequency (RF) magnetron sputtering from a CuO target. The base and working pressure was 5.0×10^{-6} Torr and 2.0×10^{-2} Torr, respectively, and the N_2 gas flow rate was $20 \text{ cm}^3/\text{min}$ throughout the evaporation process. The RF sputtering power and sputtering time were 100 W and 20 min, respectively.

The structure and morphology of the nanorod samples were characterized by scanning electron microscopy (SEM, Hitachi S-4200, Billerica, MA, USA), transmission electron microscopy (TEM, Philips CM-200, Eindhoven, the Netherlands), and selected area electron diffraction. X-ray diffraction (XRD, Philips X'pert MRD, Eindhoven, the Netherlands) patterns were performed using $\text{Cu K}\alpha$ radiation (0.15406 nm). Energy-dispersive X-ray spectroscopy (EDS) was carried out to examine the elemental composition of the core-shell nanorod samples. The resistance of multiple networked pristine TeO_2 nanorod and TeO_2 / CuO core-shell nanorod sensors were measured using a Keithley source meter-2612 at a source voltage of 10 V at 150°C and 50% RH. The 50% relative humidity might be somewhat high for sensing tests. A flow-through technique was used to test the gas sensing properties. NO_2 gas diluted with synthetic air at different ratios was injected into the testing tube at a constant flow rate of $200 \text{ cm}^3/\text{min}$. The detailed procedures for sensor fabrication and the sensing test are reported elsewhere [18].

Results and discussion

Figure 1a shows a SEM image of the TeO_2 / CuO core-shell nanorods prepared by thermal evaporation followed

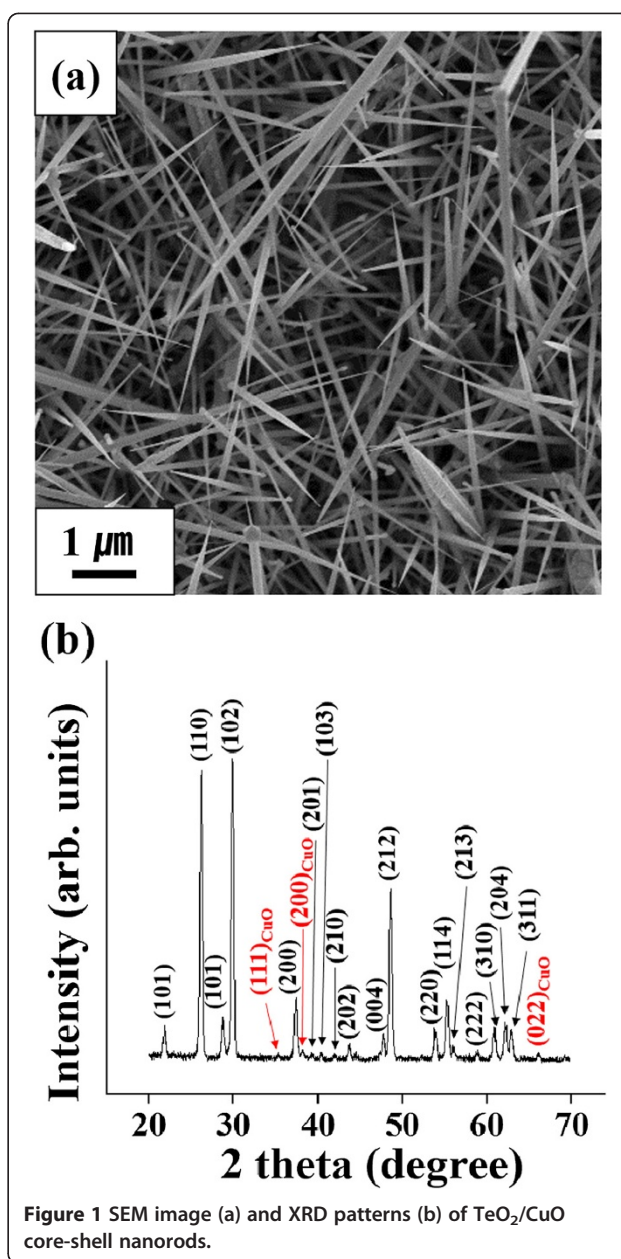

by sputtering. Each 1D nanostructure exhibited a rod-like morphology with a sharp tip, i.e. a bamboo leaf-like morphology. The core-shell nanorods were 100 to 300 nm in diameter and up to 30 μm in length. XRD was performed to determine the crystal structures of the core-shell nanorods. The XRD patterns of the TeO_2 / CuO core-shell nanorods showed that the TeO_2 cores were crystalline, whereas the CuO shells were polycrystalline (Figure 1b). Most of the XRD peaks of the TeO_2 / CuO core-shell nanorods were assigned to be the reflections of primitive tetragonal-structured rutile-

type TeO_2 . In addition, three small reflection peaks were assigned to the 111, 200, and 022 reflections of monoclinic-structured CuO with lattice constants of $a = 0.4689$ nm, $b = 0.342$ nm, $c = 0.513$ nm, and $\beta = 99.57^\circ$ (JCPDS No. 89–5899).

The low-magnification TEM image of a typical core-shell nanorod showed that the nanorod had a uniform diameter along its length direction (Figure 2a). TEM revealed a shell width of approximately 7 nm. A close examination of the high-resolution TEM (HRTEM) image (Figure 2b) shows a fringe pattern in the core region (the lower darker region), suggesting it to be a single crystal. The clear spots in the corresponding selected area electron diffraction (SAED) pattern were assigned to the primitive tetragonal structured TeO_2 with lattice constants of $a = 0.4810$ nm and $c = 0.7613$ (JCPDS No. 78–1713) (Figure 2c). On the other hand, the halo-like concentric ring pattern might be due to the polycrystalline CuO shell. The line-scanning EDS concentration profile along the diameter of a typical core-shell nanorod (Figure 2d) revealed a higher Te concentration in the center region and a higher Cu concentration in both edge regions of the nanorod, confirming the TeO_2 -core/CuO-shell structure.

Figure 3a,b shows the dynamic electrical responses of pristine TeO_2 nanorods and TeO_2/CuO core-shell nanorods, respectively, to NO_2 at 150°C under 50% RH. The sensors were exposed to successive pulses of 0.5- to 10-ppm NO_2 gas. The relative response of the p-type TeO_2/CuO nanorod sensors is defined as R_a/R_g for NO_2 , where R_a and R_g are the electrical resistances in the sensors in air and target gas, respectively. In all cases, the resistance returned to its original value after the NO_2 gas flow was switched off, confirming the reversibility of the gas absorption and desorption processes. The pristine TeO_2 nanorods showed responses of approximately 123% to 203% to NO_2 at 0.5 to 10 ppm (Table 1). In contrast, the TeO_2/CuO core-shell nanorods showed 1.2- to 2.1-fold stronger responses to NO_2 than pristine TeO_2 nanorod sensors at the same concentrations.

Figure 3c compares the response to NO_2 gas between pristine TeO_2 nanorods and TeO_2/CuO core-shell nanorods in the NO_2 concentration range below 10 ppm. The response of an oxide semiconductor sensor can be expressed as $R = A [C]^n + B$, where A and B , n , and $[C]$ are constants, exponent, and target gas concentration, respectively [19]. Data fitting gave $R = 7.52 [C] + 132.5$ and $R = 27.48 [C] + 153.9$ for the pristine TeO_2 nanorod


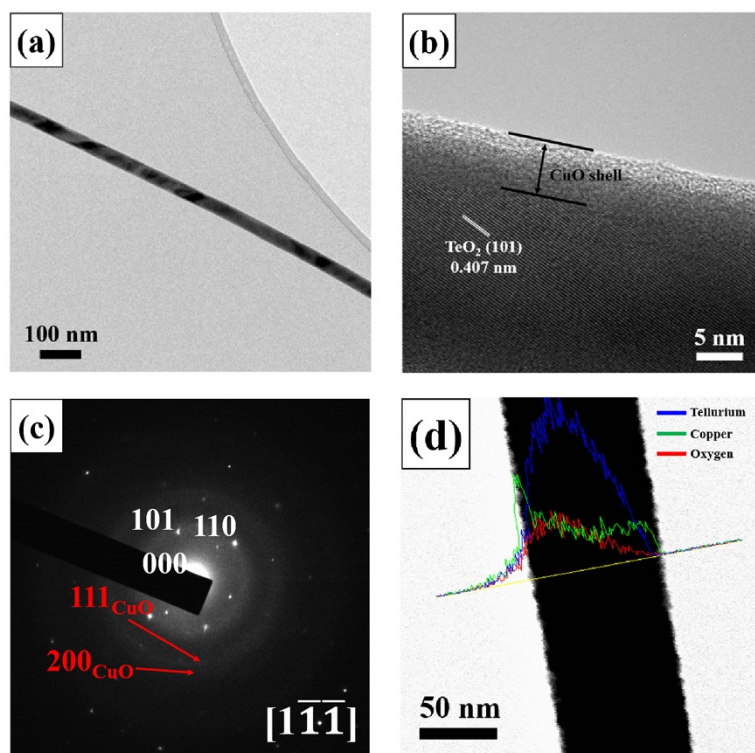


Figure 2 TEM images, diffraction pattern, and profile of TeO_2/CuO core-shell nanorods. (a) Low-magnification TEM image, (b) high-resolution TEM image, (c) selected area electron diffraction pattern, and (d) EDS line scanning concentration profile of TeO_2/CuO core-shell nanorods.

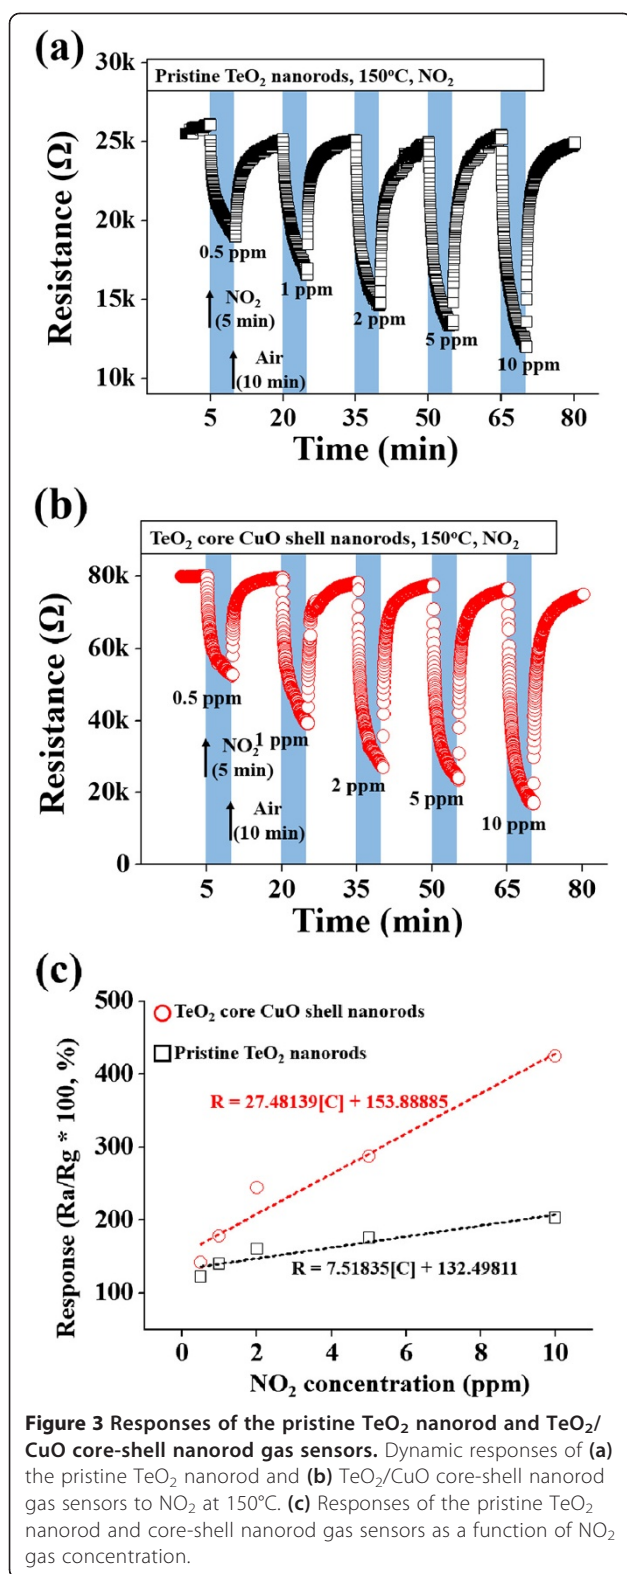

and TeO₂-core/CuO-shell nanorod sensors, respectively. The core-shell nanorod sensor showed stronger response and higher increasing rate in response to NO₂

Table 1 Responses of the TeO₂/CuO nanorod sensor to NO₂ gas at different concentrations at 150°C

NO ₂ concentration	Response (R _a /R _g , %)	
	Pristine TeO ₂ nanorod	TeO ₂ /CuO nanorod
0.5 ppm	122.60	142.17
1 ppm	140.27	178.73
2 ppm	160.08	244.24
5 ppm	175.51	287.80
10 ppm	203.12	424.91

gas at lower concentrations than the pristine nanorod sensor.

Table 2 lists the responses of the multiple networked pristine TeO₂ nanorod sensor to NO₂ gas along with those of other reported nanomaterial sensors. Overall, the sensing properties of the TeO₂/CuO core-shell nanorod sensor fabricated in this study were comparable to those of other competing nanomaterials (Table 2), but the sensing test conditions such as operating temperature, gas concentration, etc. were different [20-31]. It should be noted that the NO₂ concentration and the test temperature used in this study were mostly lower than those elsewhere. The responses of pristine TeO₂ nanorods and TeO₂-CuO nanorods to NO₂ measured in this study were stronger than those of other metal oxides such as ZnO fibers, ZnO fibre mats, mesoporous WO₃ thin film, and CdO nanowire measured at temperatures lower than 150°C. The response of WO₃-doped SnO₂ thin film was stronger to 500 ppm of NO₂ than those of pristine TeO₂ nanorods and TeO₂-CuO nanorods to 10 ppm of NO₂, but it should be noted that the former response was obtained to a far higher concentration of NO₂. TiO₂ nanofibers, SnO₂ hollow spheres, and Ru-doped SnO₂ nanowire showed stronger responses to NO₂ than those of pristine TeO₂ nanorods and TeO₂-CuO nanorods, but their operation temperatures of the former were higher than 150°C. Pristine TeO₂ nanorods and TeO₂-CuO nanorods showed stronger responses than other metal oxide nanostructures except the above-mentioned nanomaterials.

Figure 4a shows the responses of the pristine TeO₂ nanorod and TeO₂/CuO core-shell nanorod sensors to NO₂ gas as a function of the operating time. The optimum operation temperature of TeO₂/CuO core-shell nanorod sensor was 150°C, whereas that of the pristine TeO₂ nanorod sensor was 175°C. This result reveals that encapsulation of TeO₂ nanorods with a CuO thin film resulted in a 25°C decrease in operation temperature. Figure 4b exhibits the selectivity of the pristine and Bi₂O₃ nanoparticle-decorated In₂O₃ nanorod sensors to NO₂ gas over other gases. The sensors


Table 2 Comparison of the responses of the TeO₂/CuO core-shell nanorod sensor with those of other oxide 1D nanostructure sensors

Nanomaterial	Temperature (°C)	NO ₂ concentration (ppm)	Response (%)	Reference
TeO ₂ nanorods	150	0.5	123	Present work
TeO ₂ nanorods	150	10	203	Present work
TeO ₂ -CuO nanorods	150	0.5	142	Present work
TeO ₂ -CuO nanorods	150	10	425	Present work
ZnO nanorods	300	0.1	35	[20]
ZnO nanowire	250	20	>95	[21]
ZnO nanobelt	350	8.5	81	[22]
ZnO fibers	100	0.4	50	[23]
WO ₃ -core/ZnO-shell nanorods	300	5	281	[24]
TiO ₂ nanofibers	300	0.25	7,430	[25]
In-doped SnO ₂ nanoparticles	250	500	100	[26]
SnO ₂ nanoribbon	RT	3	116	[27]
SnO ₂ hollow spheres	160	5	1,150	[28]
Ru-doped SnO ₂ nanowire	150	200	>3,000	[29]
WO ₃ -doped SnO ₂ thin film	100	500	2,210	[30]
In ₂ O ₃ nanowires	400	50	360	[31]
In ₂ O ₃ nanowires	250	50	200	[32]
WO ₃ nanorods	300	1	200	[33]
Au-doped WO ₃ powders	150	10	350	[34]
Mesoporous WO ₃ thin film	100	3	>200	[35]
MoO ₃ lameller	180 to 300	10	118	[36]
CdO nanowire (porous)	100	150	>150	[37]
SnO ₂ -core/ZnO-shell nanofibers	300	70 to 2,000	20 to 320	[38]
ZnGa ₂ O ₄ -core/ZnO-shell nanowires	250	1	260	[39]

showed the highest response to ethanol among different gases at the same concentration of 200 ppm at 150°C.

The underlying mechanism of the enhanced TeO₂/CuO core-shell nanorods can be explained using a barrier-controlled carrier transport mechanism [9,10]. Potential barriers form at three places in the multiple networked TeO₂/CuO core-shell nanorod sensor: at the core-shell interface, the shell grain boundary [40], and the nanorod-nanorod contact. First, the potential barrier at core-shell interface is due to the high density of interface states in the TeO₂-CuO interfacial region. The carriers near the interface are trapped by interface states, so that a depletion layer forms over the TeO₂ core region near the interface to the CuO shell region near the interface. In addition to depletion layer formation, a potential barrier is created at the core-shell interface due to the carrier trapping as shown in Figure 5a [41]. The potential barrier is drawn in the negative energy direction, i.e. the downward direction in Figure 5a because the carriers trapped in the interface are mostly holes


residing in p-type TeO₂ core and the p-type CuO shell in the vicinity of the core-shell interface. The other two potential barriers that should be overcome by carriers on their pathways before they reach the electrode of the sensor are at the CuO-CuO homojunction, where two nanorods contact each other (Figure 5b) and at the grain boundary in the polycrystalline CuO shell layers (Figure 5a). The contributions of these two potential barriers might be smaller than that of the potential barrier at the TeO₂-CuO interface because of much smaller numbers of grain boundaries and nanorod-nanorod contacts compared to that of the core-shell interfaces. Each nanorod has a core-shell interface, whereas a CuO shell contains a small number of grain boundaries because it is as thin as approximately 7 nm and the possibility of two nanorods contacting each other in a multiple networked nanorod sensor is generally quite low. Carrier transport is facilitated or restrained because of these energy barriers by adsorption and desorption of gas molecules, resulting in a larger change in resistance, i.e., an enhanced response

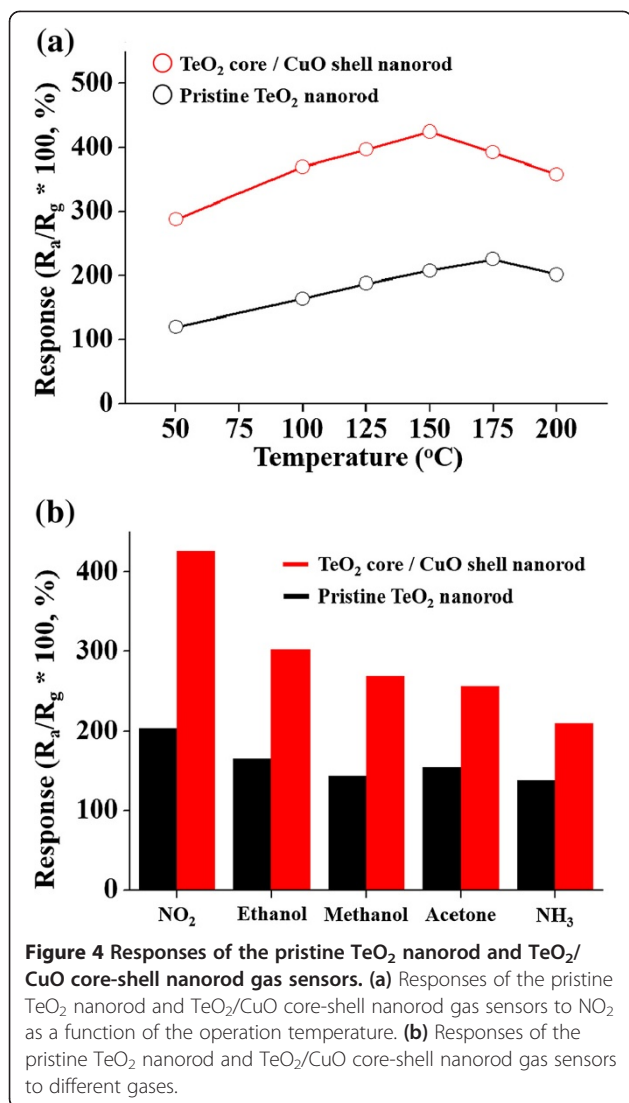

of the core-shell nanorod sensor to NO_2 gas. In other words, the heights of the potential barriers are modulated at the three places, resulting in enhanced response of the sensor to the gas.

Conclusions

TeO₂/CuO core-shell nanorods were synthesized using a two-step process: the synthesis of TeO₂ nanorods by thermal evaporation of Te powder and sputter deposition of CuO. The cores and shells of the nanorods were single crystal TeO₂ and polycrystalline CuO, respectively. The responses of the TeO₂ nanorods to NO_2 were improved approximately 2.1- to 2.1-fold at NO_2 concentrations of 0.5 to 10 by coating them with CuO. The responses of the core-shell nanorods to NO_2 gas were also comparable or superior to those of the other

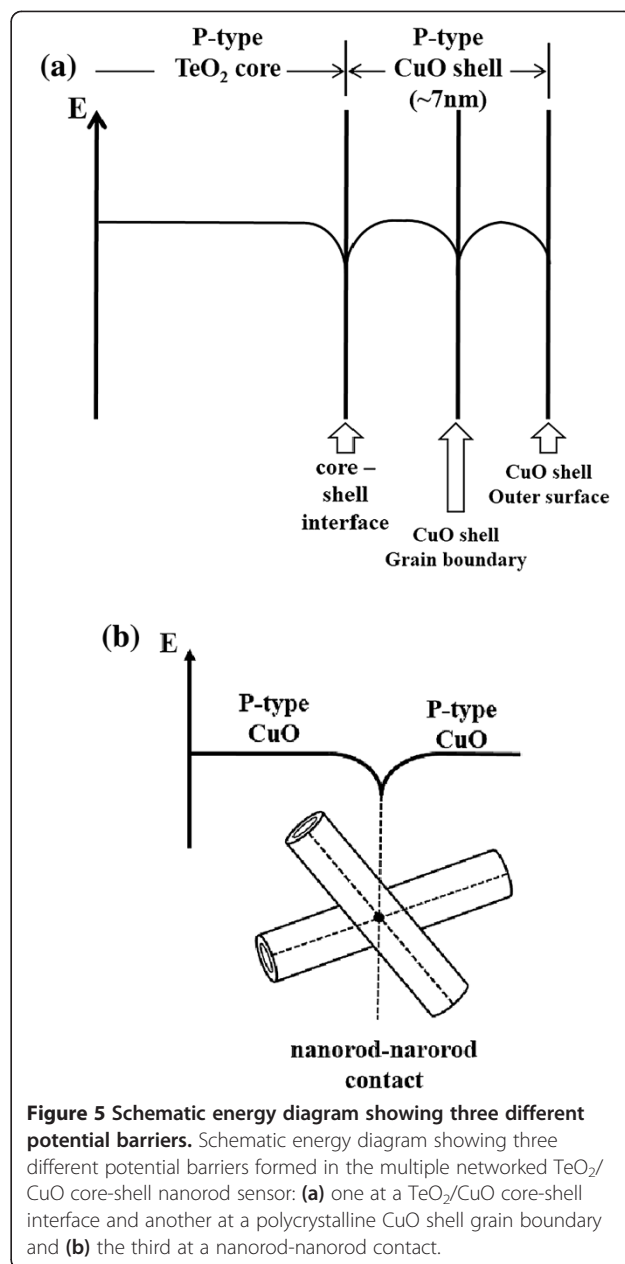

metal oxide semiconductor nanostructured sensors reported previously. The enhanced response of the TeO₂/CuO core-shell nanorods to NO_2 gas may be due to modulation of the heights of the potential barriers formed at three different places in the multiple networked 1D nanostructure sensor: the TeO₂ core-CuO shell interface, the CuO-CuO homojunction at the contact of two core-shell nanorods, and the grain boundaries in the polycrystalline CuO shell layers.

Competing interests

The authors declare that they have no competing interests.

Authors' contributions

All the authors contributed equally to the paper. All authors read and approved the final manuscript.

Acknowledgements

This study was supported by the 2010 Core Research Program through the National Research Foundation of Korea (NRF) funded by the Ministry of Education, Science and Technology.

Author details

¹Department of Materials Science and Engineering, Inha University, 253 Yonghyun-dong, Nam-gu, Incheon 402-751, Republic of Korea. ²Department of Chemistry, Inha University, 253 Yonghyun-dong, Nam-gu, Incheon 402-751, Republic of Korea. ³Department of Nanooptical Engineering, Korea Polytechnic University, 2121 Jeongwangdong, Shiheung-city, Gyeonggi-do 429-793, Republic of Korea.

Received: 26 August 2014 Accepted: 14 November 2014

Published: 27 November 2014

References

- Tippins HH: Optical absorption and photoconductivity in the band edge of β -Ga₂O₃. *Phys Rev A* 1965, **140**:316–319.
- Yamazoe N: New approaches for improving semiconductor gas sensors. *Sens Actuators B* 1991, **5**:7–19.
- Gundiah G, Govindaraj A, Rao CNR: Nanowires, nanobelts and related nanostructures of Ga₂O₃. *Chem Phys Lett* 2002, **351**:189–194.
- Zhang HZ, Kong YC, Wang YZ, Du X, Bai ZG, Wang JJ, Yu DP, Ding Y, Hang QL, Feng SQ: Ga₂O₃ nanowires prepared by physical evaporation. *Sol State Comm* 1999, **9**:677–682.
- Kim BC, Sun KT, Park KS, Im KJ, Noh T, Sung MY, Kim S, Nahm S, Choi YN, Park SS: β -Ga₂O₃ nanowires synthesized from milled GaN powders. *Appl Phys Lett* 2002, **80**:479–481.
- Yan C, Le BH, Kang DJ: Ultrasensitive single crystalline TeO₂ nanowire based hydrogen gas sensors. *J Mater Chem A* 2014, **2**:5394–5398.
- Sanchez-Castillo MA, Couto C, Kim WB, Dumesic JA: Gold-nanotube membranes for the oxidation of CO at gas-water interfaces. *Angew Chem Int Ed* 2004, **43**:1140–1142.
- Jagerszki G, Giurskisany RE, Hoeffler L, Pretsch E: Hybridization-modulated ion fluxes through peptide-nucleic-acid-functionalized Gold nanotubes. A new approach to quantitative label-free DNA analysis. *Nano Lett* 2007, **7**(6):1609–1612.
- Wang W, Li Z, Zheng W, Huang H, Wang C, Sun J: Cr₂O₃-sensitized ZnO electrospun nanofibers based ethanol detectors. *Sens Actuators B* 2010, **143**:754–758.
- Sun P, Sun Y, Ma J, You L, Lu G, Fu W, Li M, Yang H: Synthesis of novel SnO₂/ZnSnO₃ core-shell microspheres and their gas sensing properties. *Sens Actuators B* 2011, **155**:606–611.
- Wang L, Kang Y, Wang Y, Zhu B, Zhang S, Huang W: CuO nanoparticle decorated ZnO nanorod sensor for low-temperature H₂S detection. *Mater Sci Eng C* 2012, **32**:2079–2085.
- Liu Y, Zhu G, Chen J, Xu H, Shen X, Yuan A: Co₃O₄/ZnO nanocomposites for gas-sensing applications. *Appl Surf Sci* 2013, **265**:379–384.
- Kusior A, Radecka M, Rekas M, Lubecka M, Zakrzewska K, Reszka A: Sensitization of gas sensing properties in TiO₂/SnO₂ nanocomposites. *Procedia Eng* 2012, **47**:1073–1076.
- De Lacy Costello BPJ, Ewen RJ, Ratcliffe NM, Sivanand PS: Thick film organic vapour sensors based on binary mixtures of metal oxides. *Sens Actuators B* 2003, **92**:59–166.
- Kim ID, Rothschild A, Lee BH, Kim DY, Jo SM, Tuller HL: Ultrasensitive chemiresistors based on electrospun TiO₂ nanofibers. *Nano Lett* 2006, **6**:2009–2013.
- Jin C, Park S, Kim H, Lee C: Enhanced gas sensing properties of Pt-loaded TeO₂ nanorods. *Bull Kor Chem Soc* 2012, **33**:1851–1855.
- Li YJ, Li KM, Wang CY, Kuo CI, Chen LJ: Low-temperature electrodeposited Co-doped ZnO nanorods with enhanced ethanol and CO sensing properties. *Sens Actuators B* 2012, **161**:734–739.
- Jin C, Park S, Kim H, Lee C: Ultrasensitive multiple networked Ga₂O₃-core/ZnO-shell nanorods gas sensors. *Sens Actuators B* 2012, **161**:223–228.
- Williams DE: *Solid State Gas Sensors*. Bristol: Hilger; 1987.
- Oh E, Choi HY, Jung SH, Cho S, Kim JC, Lee KH, Kang SW, Kim J, Yun JY, Jeong SH: High-performance NO₂ gas sensor based on ZnO nanorod grown by ultrasonic irradiation. *Sens Actuators B* 2009, **141**:239–243.
- Ahn MW, Park KS, Hoe JH, Park JG, Kim DW, Choi KJ, Lee JH, Hong SH: Gas sensing properties of defect-controlled ZnO-nanowire gas sensor. *Appl Phys Lett* 2008, **93**:263103.
- Sadek AZ, Choopun S, Wlodarski W, Ippolito SJ, Kalantar-zadeh K: Characterization of ZnO nanobelt-based gas sensor for H₂, NO₂, and hydrocarbon sensing. *IEEE Sens J* 2007, **7**:919–924.
- Baratto C, Sberveglieri G, Onisichuk A, Caruso B, Stasio SD: Low temperature selective NO₂ sensors by nanostructured fibres of ZnO. *Sens Actuators B* 2004, **100**:261–265.
- Ahn S, Park S, Ko H, Lee C: Enhanced NO₂ gas sensing properties of WO₃ nanorods encapsulated with ZnO. *Appl Phys A* 2012, **108**:53–58.
- Landau O, Rothschild A, Zussman E: Processing-microstructure-properties correlation of ultrasensitive gas sensors produced by electrospinning. *Chem Mater* 2009, **21**:9–11.
- Kaur J, Kumar R, Bhatnagar MC: Effect of indium-doped SnO₂ nanoparticles on NO₂ gas sensing properties. *Sens Actuators B* 2007, **126**:478–484.
- Law M, Kind H, Messer B, Kim F, Yang P: Photochemical sensing of NO₂ with SnO₂ nanoribbon nanosensors at room temperature. *Angew Chem Int Ed* 2002, **41**:2405–2408.
- Zhang J, Wang S, Wang Y, Wang Y, Zhu B, Xia H, Guo X, Zhang S, Huang W, Wu S: NO₂ sensing performance of SnO₂ hollow-sphere sensor. *Sens Actuators B* 2009, **135**:610–617.
- Ramgir NS, Mulla IS, Vijayamohan KP: A room temperature nitric oxide sensor actualized from Ru-doped SnO₂ nanowires. *Sens Actuators B* 2005, **107**:708–715.
- Kaur J, Roy SC, Bhatnagar MC: Highly sensitive SnO₂ thin film NO₂ gas sensor operating at low temperature. *Sens Actuators B* 2007, **123**:1090–1095.
- Vomiero A, Bianchi S, Comini E, Faglia G, Ferroni M, Sberveglieri G: Controlled growth and sensing properties of In₂O₃ nanowires. *Cryst Growth Des* 2007, **7**:2500–2504.
- Xu P, Cheng Z, Pan Q, Xu J, Xiang Q, Yu W, Chu Y: High aspect ratio In₂O₃ nanowires: synthesis, mechanism and NO₂ gas-sensing properties. *Sens Actuators B* 2008, **130**:802–808.
- Liu Z, Miyauchi M, Yamazaki T, Shen Y: Facile synthesis and NO₂ gas sensing of tungsten oxide nanorods assembled microspheres. *Sens Actuators B* 2009, **140**:514–519.
- Xia H, Wang Y, Kong F, Wang S, Zhu B, Guo X, Zhang J, Wu S: Au-doped WO₃-based sensor for NO₂ detection at low operating temperature. *Sens Actuators B* 2008, **134**:133–139.
- Teoh LG, Hon YM, Shieh J, Lai WH, Hon MH: Sensitivity properties of a novel NO₂ gas sensor based on mesoporous WO₃ thin film. *Sens Actuators B* 2003, **96**:219–225.
- Rahmani MB, Keshmiri S, Yu J, Sadek A, Al-Moafi A, Latham K, Li Y, Wlodarski W, Kalantar-Zadeh K: Gas sensing properties of thermally evaporated lamellar MoO₃. *Sens Actuators B* 2010, **145**:13–19.
- Guo Z, Li M, Liu J: Highly porous CdO nanowires: preparation based on hydroxy-and carbonate-containing cadmium compound precursor nanowires, gas sensing and optical properties. *Nanotechnology* 2008, **19**:245611.
- Choi SW, Park JY, Kim SS: Synthesis of SnO₂-ZnO core-shell nanofibers via a novel two-step process and their gas sensing properties. *Nanotechnology* 2009, **20**:465603–465608.
- Chen IC, Lin SS, Lin TJ, Hsu CL, Hsueh TJ, Shieh TY: The assessment for sensitivity of a NO₂ gas sensor with ZnGa₂O₄/ZnO core-shell nanowires-a novel approach. *Sensors* 2010, **10**:3057–3072.
- Xu C, Tamaki J, Miura N, Yamazoe N: Grain size effect on gas sensitivity of porous SnO₂-based elements. *Sens Actuators B* 1991, **3**:147–155.
- Park S, Ko H, Kim S, Lee C: Role of the interfaces in multiple networked one-dimensional core-shell nanostructured gas sensors. *ACS Appl Mater Interfaces* 2014, **6**:9595–9600.

doi:10.1186/1556-276X-9-638

Cite this article as: Park et al.: Fabrication and NO₂ gas sensing performance of TeO₂-core/CuO-shell heterostructure nanorod sensors. *Nanoscale Research Letters* 2014 **9**:638.